

Powder Metallurgy High-Speed Steel ASP® 2030

ERASTEEL



ASP® 2030 is a cobalt grade for high performance cutting and cold work tools.

STANDARDS

- > EN 10027-1: PMHS 6-5-3-8
- > EN 10027-2: 1.3294
- > SWEDEN: SS 2726

DELIVERY HARDNESS

- > Typical soft annealed hardness is 290 HB
- > Cold-drawn and cold-rolled material is typically 10-40 HB harder

CHEMICAL COMPOSITION

Safety datasheet available

C	Cr	Mo	W	Co	V
1.28	4.2	5.0	6.4	8.5	3.1


APPLICATIONS

- > End mills
- > Hobs
- > Shaper cutters
- > Broaches
- > Bi-metal saws
- > Taps
- > Drills
- > Cold work tools
- > Fine blanking
- > Dies

HEAT TREATMENT

- > Soft annealing in a protective atmosphere at 850-900°C for 3 hours, followed by slow cooling at 10°C/h down to 700°C, then air cooling.
- > Stress-relieving at 600-700°C for approximately 2 hours, slow cooling down to 500°C.
- > Hardening in a protective atmosphere with pre-heating in 2 steps at 450-500°C and 850-900°C and austenitizing at a temperature suitable for chosen working hardness. Cooling down to 40-50°C.
- > Tempering at 560°C three times for at least 1 hour each time. Cooling to room temperature < 25°C between temperings.

GUIDELINES FOR HARDENING

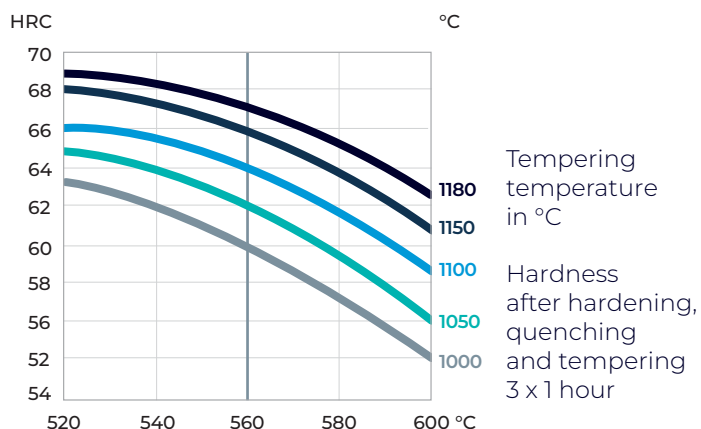

FORM SUPPLIED

- > Coils
- > Round bars
- > Flat & square bars
- > Forged blanks

Available surface conditions: drawn, ground, hot-worked, peeled, rough-machined.

PROCESSING

ASP® 2030 can be worked as follows:

- > machining (grinding, turning, milling)
- > polishing
- > hot forming
- > electrical discharge machining
- > welding (special procedure including preheating and filler materials of base material composition)

GRINDING

During grinding, local heating of the surface, which may alter the temper, must be avoided. Grinding wheel manufacturers can provide advice on the choice of grinding wheels.

SURFACE TREATMENT

The steel grade is a perfect substrate material for PVD coating. If nitriding is requested, a small diffusion zone is recommended but avoid compound and oxidized layers.



PROPERTIES


PHYSICAL PROPERTIES

Temperature	20°C	400°C	600°C
Density g/cm ³ ⁽¹⁾	8.1	7.9	7.9
Modulus of elasticity kN/mm ² ⁽²⁾	240	214	192
Thermal expansion ratio per °C ⁽²⁾	-	11.8x10 ⁻⁶	12.3x10 ⁻⁶
Thermal conductivity W/m°C ⁽²⁾	24	28	27
Specific heat J/kg°C ⁽²⁾	420	510	600

(1) Soft annealed


(2) Hardened 1180°C and tempered 560°C, 3 x 1 hour

IMPACT TOUGHNESS

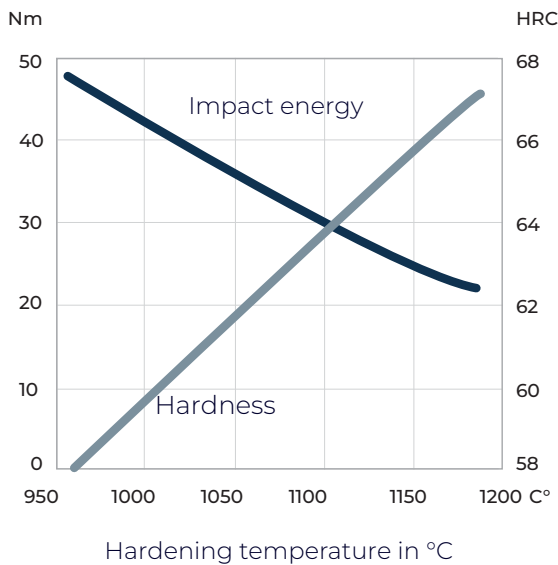

Original dimension 9 x 12 mm
Tempering 3 x 1 hour at 560°C
Unnotched test piece 7 x 10 x 55 mm


CCT CURVE

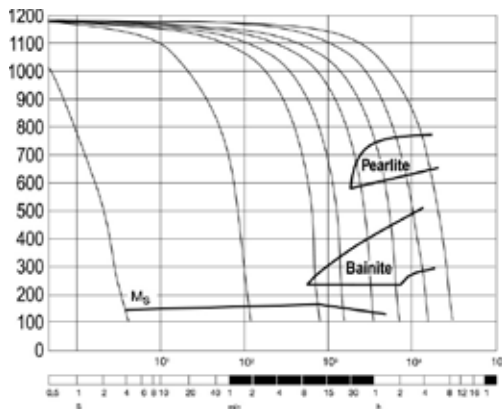

Continuous cooling transformation curve

Hardening temperature 1180°C


4-POINT BEND STRENGTH

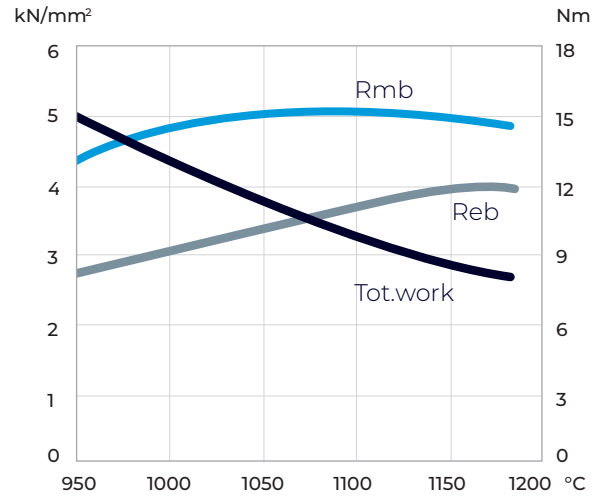

Hardening temperature in °C

Original dimension Ø 6 mm
Tempering 3 x 1 hour at 560°C
Dimension of test piece Ø 4.7 mm

Rmb = Ultimate bend strength in kN/mm²
Reb = Bend yield strength in kN/mm²
Tot. work = Total work in Nm

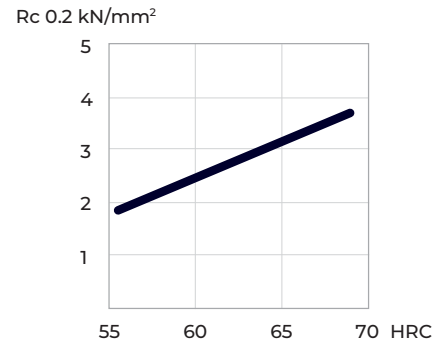

COMPARATIVE PROPERTIES

